Dow Performance Silicones

Jet Fuel Resistance Testing
Airfield Applications

DOWSIL™

As stated in FAA Engineering Brief No. 36 (dated 5/86), "The function of a sealant is to seal the joint between two concrete surfaces. Therefore, the sealant's strength characteristics are less important than its ability to withstand joint movement and maintain adhesion." This document goes on further to state that "Silicone sealant is not degraded by contact with jet fuel. Some swelling of the material will normally occur, but it will return to its original shape upon evaporation of the fuel, without loss of bond."

Generally, for a sealant to be successful in an airfield application, it must meet the following requirements:

- Resistance to ultraviolet light
- Wide temperature flexibility
- Cyclic movement capability (both extension and compression)
- Fuel/oil resistance
- Jet blast resistance

Federal Specifications SS-S-200E, SSS-S-1614A and ASTM Specification D 3569 attempt to test for the above performance requirements. However, when it comes to cyclic movement capability, they all fall short. The best cyclic movement test that closely relates to actual field conditions is ASTM C 719. See Table I for a brief comparison of these specifications.

Since there are few federal or ASTM specifications presently written for silicones, Dow developed a test method to verify that silicone sealants can meet the requirements for airfield applications mentioned above.


A simulated fuel spill test joint (see Figure 1) was chosen along with ASTM C 719 cyclic testing. This test joint in combination with C 719 appeared to be a more accurate depiction of actual field conditions.

The test consists of forming several sealant test joints between two concrete blocks with a dam on top of each block (see Figure 1). The sealant is allowed to cure. The dam is filled with the test fluid (i.e., jet fuel). The fluid is then allowed to dissipate, as it would in the field. If more than one fluid is to be tested on the same joint, then approximately one week separates each fluid application. At the end of the fluid exposure, these same test joints are then subjected to cyclic testing per the ASTM C 719 specification.

Table I. Specification Comparison

		Cyclic Movement Capability	
Specification	**Sealant Type**	**Extension**	**Compression**
SS-S-200E	Cold Applied	3 cycles @ 0°F (-17°C)	None
SS-S-1614A	Hot Applied	3 cycles @ 0°F (-17°C)	None
ASTM D 3569	Hot Applied	3 cycles @ 0°F (-17°C)	None
ASTM C 719	Cold Applied	10 cycles @ -15°F (-26°C)	10 cycles @ 158°F (70°C)

Figure 1. Simulated Fuel Spill Test Joint

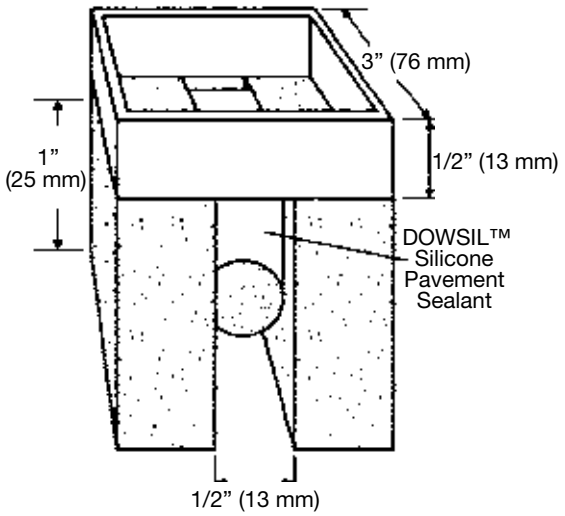

During the initial contact with some fluids, the test joints showed some visual volume increase. However, after dissipation of the fluids, these same test joints did return to their original shape (see Figure 2 and Table II). More importantly, after further subjecting the same test joints to cyclic testing (after fluid dissipation), they showed no signs of bond loss.

The airfield application test method from Dow is a good indication that DOWSIL™ silicone pavement products can provide the necessary airfield performance requirements. But the best indication is Dow's actual field track record, with applications dating back to 1980.

Figure 2. Effect of Fuel Spill on DOWSIL™ Silicone Joint Sealant

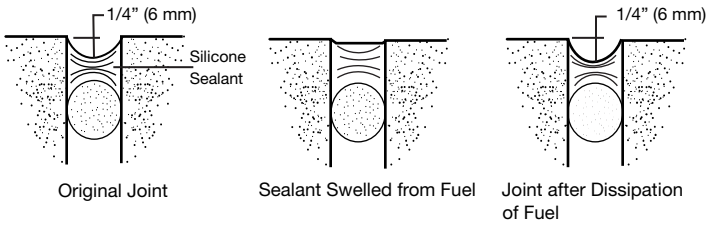


Table II. Joint Surface Volume Change

	Percent Volume Swell – Visual	
Fluid	**DOWSIL™ 888 Silicone Joint Sealant**	**DOWSIL™ 890-SL Silicone Joint Sealant**
JP-4	5 percent	15-20 percent
Jet Fuel A/A-1	5 percent	15-20 percent
50/50 Glycol/H2O	None	None
Hydraulic Fluid	None	None
Skydrol B	None	None

[1]After drying, all samples passed +100/-50 percent movement testing.

NOTICE: No freedom from infringement of any patent owned by Dow or others is to be inferred. Because use conditions and applicable laws may differ from one location to another and may change with time, Customer is responsible for determining whether products and the information in this document are appropriate for Customer's use and for ensuring that Customer's workplace and disposal practices are in compliance with applicable laws and other government enactments. The product shown in this literature may not be available for sale and/or available in all geographies where Dow is represented. The claims made may not have been approved for use in all countries. Dow assumes no obligation or liability for the information in this document. References to "Dow" or the "Company" mean the Dow legal entity selling the products to Customer unless otherwise expressly noted. NO WARRANTIES ARE GIVEN; ALL IMPLIED WARRANTIES OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE ARE EXPRESSLY EXCLUDED.

®™ Trademark of The Dow Chemical Company ("Dow") or an affiliated company of Dow

© 2022 The Dow Chemical Company. All rights reserved.

2000019231

Form No. 62-207-01-0622 S2D